

RESEARCH ON DESULPHURIZATION OF STEEL WITH CALCIUM ALUMINATE SYNTHETIC SLAG WITH ADDITION OF TITANIUM OXIDE

Adriana Puțan, Teodor Hepuț, Vasille Puțan

University "Politehnica" Timisoara,
Faculty Engineering Hunedoara,
Revoluției, 5, Hunedoara, 331128, Romania

ABSTRACT

In the practice of deoxidation with synthetic slag, we usually use the slag from the binary systems: CaO-Al₂O₃, CaO-TiO₂ and CaO-CaF₂ or from the ternary systems: CaO-SiO₂-Al₂O₃ and CaO-CaF₂-Al₂O₃. According to the literature, the best results were obtained with synthetic slag from the binary system CaO-Al₂O₃ (50-52% CaO and 38-42% Al₂O₃).

The paper presents the results of laboratory experiments on steel desulphurisation with slag from the system CaO-SiO₂-TiO₂.

To determine the influence, on the desulphurisation process, of the titanium oxide added in calcium aluminates slag, we experimented, in the laboratory phase, the steel treatment with a mechanical mixture consisting of lime, aluminous slag and slag obtained from the titanium making process through the aluminothermy technology.

The steel melting was carried out in an induction furnace of 10 kg capacity, existent in the "Metallic Melts" laboratory of the Engineering Faculty of Hunedoara.

During the research, we aimed to establish correlation equations between the sulphur distribution coefficient and the slag components (CaO, Al₂O₃, TiO₂, FeO, MgO and MnO). The data obtained in the experiments were processed in Excel and MATLAB programs, resulting simple or multiple correlation equations, which allowed the elucidation of some physical-chemical phenomena specific to the desulphurisation processes.

Keywords:

steel treatment, desulphurization, synthetic slag, calcium aluminate, titanium oxide

1. GENERAL CONSIDERATIONS

The steel refining with liquid slag or various powder mixtures of synthetic slag is based on the intensification of the unwanted impurities (sulphur, non-metallic suspensions & oxygen) passage from the liquid steel in the slag, mainly by diffusion, or partly through the entrainment of some suspensions by settling the synthetic slag particles found in the treated steel bath. The synthetic slag can be also obtained by adding mechanical mixture directly in the casting ladle; in this case, for compensating the cooling of the steel in the casting ladle due to the addition of materials (melting and superheating), the steel temperature should be at least 20-40°C higher than the normal one. In the practice of deoxidation with synthetic slag, we usually use slag that correspond to the binary systems CaO-Al₂O₃, CaO-TiO₂ and CaO-CaF₂, or to the ternary systems CaO-SiO₂-Al₂O₃ and CaO-CaF₂-Al₂O₃. According to the literature, the best results were obtained with synthetic slag that corresponds to the binary system CaO-Al₂O₃, containing 50-52% CaO and 38-42% Al₂O₃.

The viscosity of the synthetic slag has significant influence on the development of physical and chemical processes during the treatment of the liquid steel, interfering with significant weight on the emulsifying capacity of slag. The increase of the slag viscosity from 0.15 to 0.45 Ns/m² (from 1.5 to 4.5 Poise) determines the decrease with approx. 30% of the steel-slag interaction surface. Such increasing of the calcium aluminate slag viscosity can be seen when its temperature is decreasing (for example, from 1600°C to 1470°C). Therefore, it is very important to ensure, during processing the steel with liquid slag, the optimum thermal regime specific to the chosen slag type and to realise its convenient fluidity (viscosity).

At the temperatures of treating the steel with synthetic slag in the ladle, the minimum viscosity corresponds to the slag with 56% CaO. But, taking into account the fact that frequent deviations (1-2%) may occur from this optimum composition under industrial conditions, we should also consider the danger of reaching unwanted values (higher than 57% CaO). Therefore, in the industrial practice it is recommendable a content of 52-54% CaO in slag, for which the normal composition deviations can't provoke sudden viscosity increases.

The viscosity of the synthetic slag is also influenced by other components; it increases significantly with the increasing of the SiO₂ content, while MgO contents up to 8% are favourable. At temperatures higher than 1500°C, the viscosity is slightly decreasing when adding TiO₂ in the calcium aluminate slag.

Usually, the chemical composition of the synthetic slag that corresponds to the CaO – Al₂O₃ system, frequently used in practice, varies between the following limits: CaO = 48 – 55%; Al₂O₃ = 40 – 45%; SiO₂ = maximum 3.0%; MgO = maximum 3% and FeO = maximum 1%, the balance being other oxides.

Because the diffusion speed in slag increases with increasing temperature (T) and decreasing viscosity (η), we can highlight the special importance of the synthetic slag viscosity (i.e. its fluidity $\varphi=1/\eta$) in the process of treating the steel with synthetic slag. Similarly, the bigger is the contact surface between the synthetic slag and the metallic bath, the faster is the passage of the significant elements to the slag, the contact surface being, along with the viscosity, another determinant element in treating the steel with synthetic slag.

2. LABORATORY EXPERIMENTS

To determine the influence, on the desulphurisation process, of the addition of titanium oxide in the calcium aluminate slag, we performed laboratory experiments, i.e. we treated the slag with liquid synthetic slag obtained by melting the mixture consisting of limestone, aluminate slag and slag obtained from the titanium making process through the aluminothermic technology.

The steel melting was carried out in an induction furnace of 10 kg capacity and the slag melting was carried out in a crucible furnace, both existent in the "METALLIC MELTS" laboratory of the Engineering Faculty of Hunedoara.

The charge to be melted consisted *of steel samples* (samples of steel for tubes, taken from the casting ladle before the LF treatment, i.e. before introducing the steel in the LF).

To form the liquid synthetic slag, we melted in the crucible furnace a mechanical mixture consisting of limestone, calcium aluminate slag (from melting the aluminium scrap) and slag obtained from the titanium making process through the aluminothermic technology. The steel quantity obtained was 10 kg/heat, and the addition of liquid slag was 3% (300 g/heat). The

synthetic slag was added directly in the casting ladle; so, the slag reached the ladle before the steel, ensuring a good mix between the two melts. To determine the sulphur distribution coefficient, we took steel and slag samples before and after the treatment, to find the sulphur content and the chemical composition. We also measured the steel and slag temperature before and after the treatment.

3. RESULTS OBTAINED FROM PROCESSING THE EXPERIMENTAL DATA

By processing the data obtained in the laboratory phase, we obtained equations of correlation between the chemical composition of the synthetic slag and the sulphur distribution coefficient (L.S.). The data were processed in Excel and MATLAB programs, the results being presented hereunder, in graphical and analytical forms.

In Fig. 1, we can see that a TiO_2 content increase up to 5-6% leads to the increasing of the L.S., fact explicable, from a technological point of view, through to the positive influence of the titanium oxide on the slag fluidity, especially at temperatures above $1500^{\circ}C$. Therefore, we recommend contents of 3-6% TiO_2 in the refining slag.

In Fig. 2, we see that the increase of the MgO content up to approx. 8% leads to the increasing of the L.S., fact explicable, from a technological point of view, by the favourable influence of this oxide on the viscosity (the viscosity is decreasing). Therefore, from a technological point of view, we recommend the maximum MgO content to be 6%.

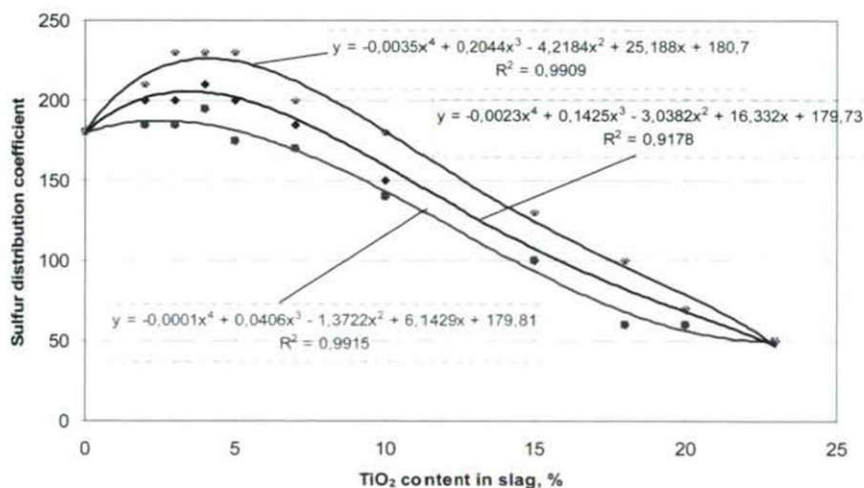


Fig.1 The variation of the sulphur distribution coefficient versus the TiO_2 content in slag

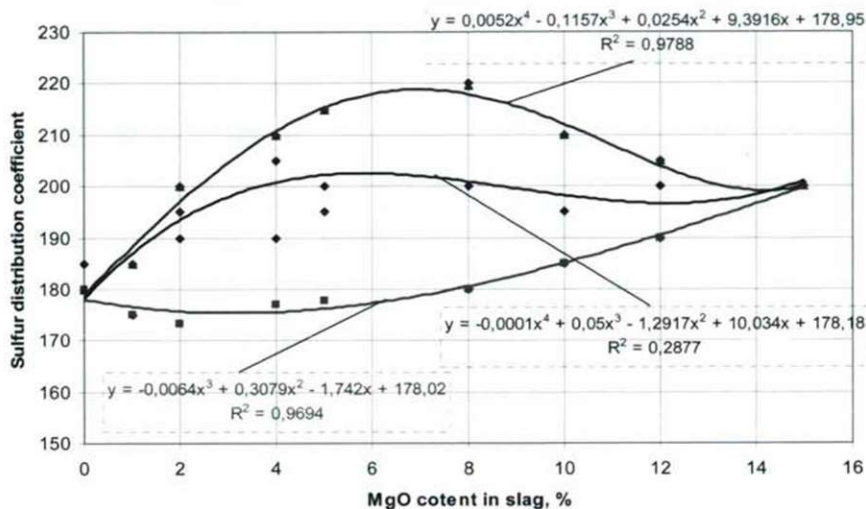


Fig.2 The variation of the sulphur distribution coefficient versus the MgO content in slag

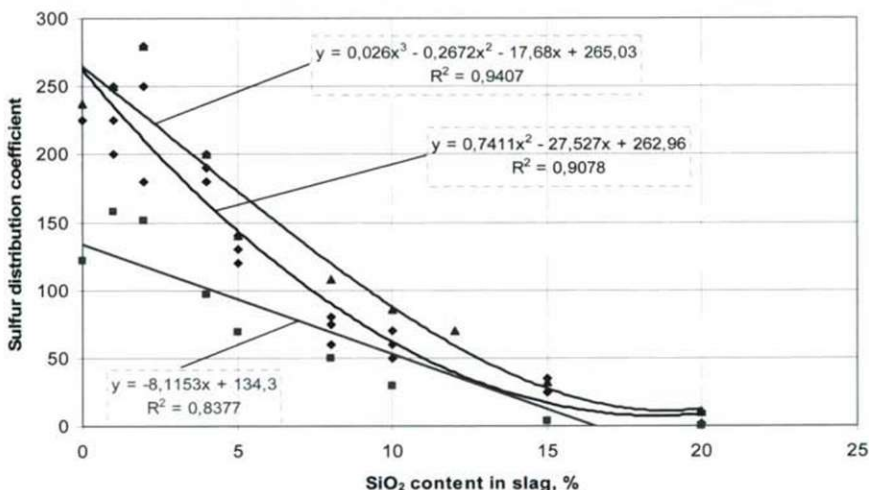


Fig.3 The variation of the sulphur distribution coefficient versus the SiO₂ content in slag

In Fig. 3, we see that the increasing of the SiO₂ content leads to the decreasing of the L.S., which can be explained, from a technological point of view, on the one hand by the slag viscosity increasing with the SiO₂ content increasing and, on the other hand, by the decreasing of the free CaO content, the main oxide in slag that directly participates to the desulphurisation process. From the graphical representation, we can see that, when the SiO₂ content is increasing, the variation range of the L.S. becomes narrower and narrower, especially for values higher than 5%. Technologically, we recommend the maximum SiO₂ content to be 3%.

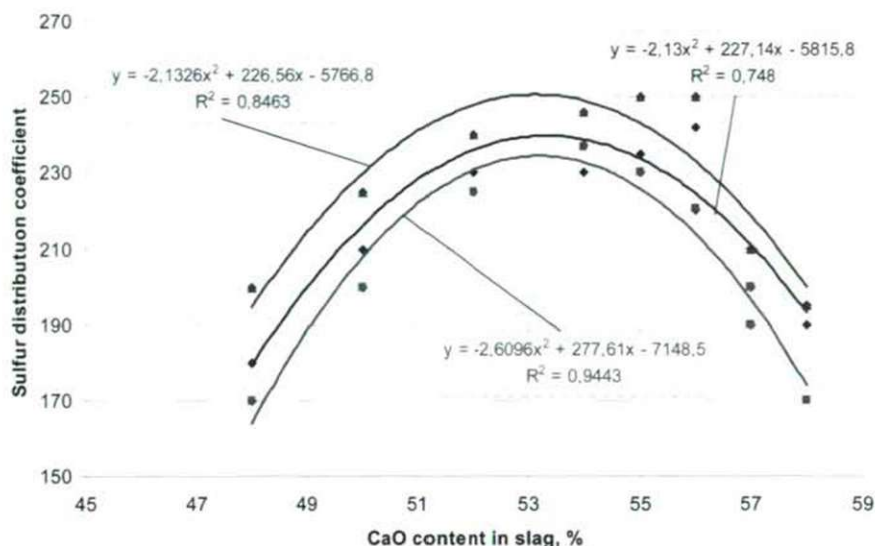


Fig.4 The variation of the sulphur distribution coefficient versus the CaO content in slag

The graphical representation presented in Fig. 4 shows that the higher values for the L.S. (230-250) were obtained for a CaO content of 52 -54%. According to the data presented in the literature [2] the minimum viscosity of the slag that corresponds to the CaO – Al₂O₃ system is obtained for contents of approx. 56% CaO, which confirms the results obtained for the slag used in our experiments. The CaO contents higher than 55%, determine the decreasing of the L.S. values, because the slag viscosity is increasing. Having in view that, in industrial conditions, there are frequent deviations from the above mentioned range of chemical composition, we recommend contents of 52-56% CaO.

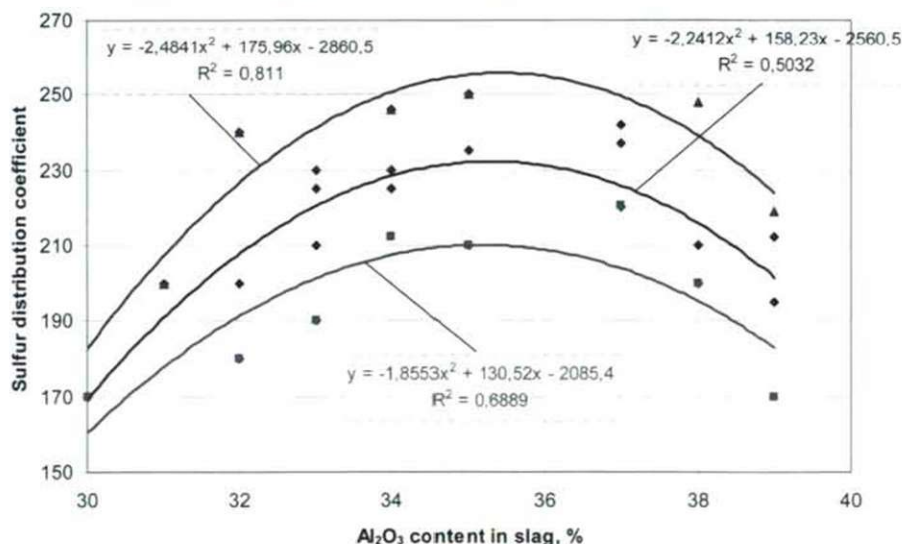


Fig.5 The variation of the sulphur distribution coefficient versus the Al₂O₃ content in slag

Analysing the graphical representation presented in Fig.5, we can see a variation in the L.S. depending on the Al_2O_3 content, similar to the variation depending on the CaO content in slag. The maximum L.S. value was obtained at 34–37% Al_2O_3 . The increasing of the aluminium oxide content up to values that vary between the above mentioned limits is due to the decreasing of the slag viscosity and, in consequence, the intensification of the sulphur diffusion in the slag bath. The increasing of the Al_2O_3 content beyond the above mentioned limits determines the decreasing of the L.S. values, as a consequence of the slag viscosity increasing. We recommend contents of 33-37% Al_2O_3 in slag.

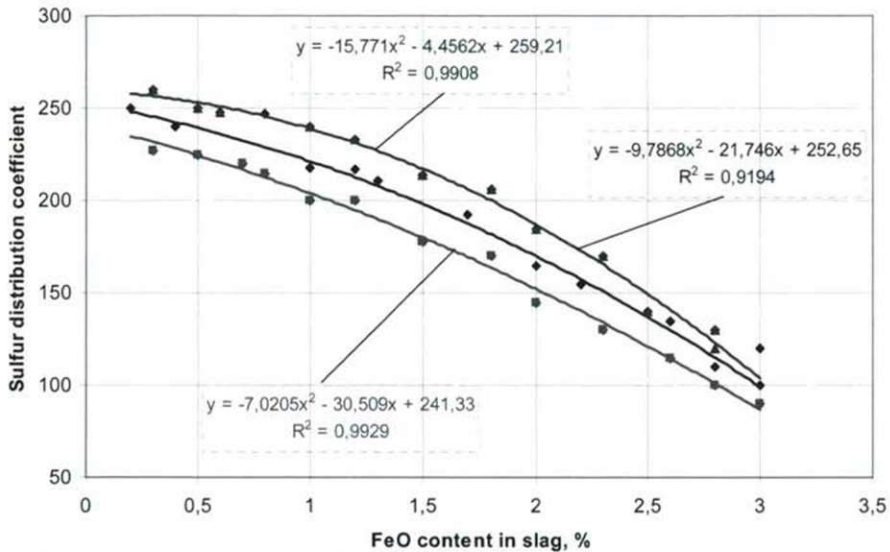


Fig.6 The variation of the sulphur distribution coefficient versus the FeO content in slag

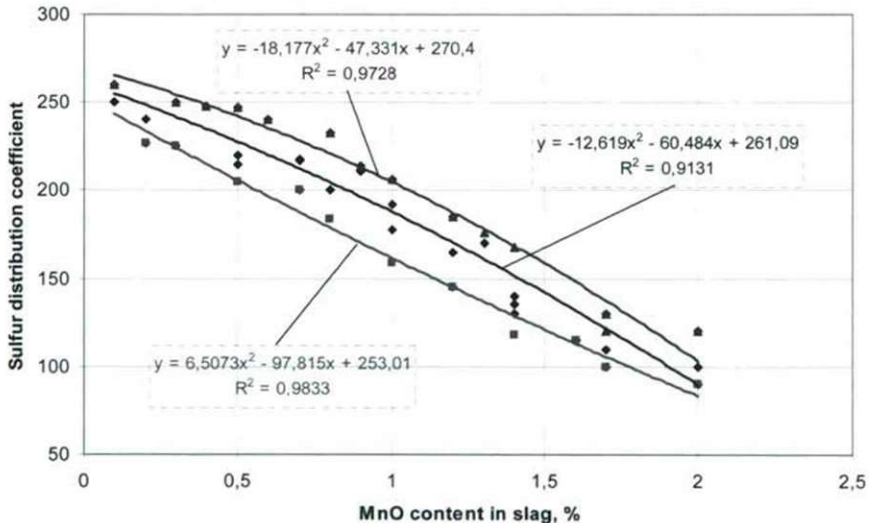


Fig.7 The variation of the sulphur distribution coefficient versus the MnO content in slag

From the graphical correlations presented in Fig. 6 and 7, we can see that the increasing of the FeO and MnO contents in slag leads to the decreasing of the L.S., which is consistent with the fact that the steel desulphurisation is encouraged by strong basic slag (which presents high $[O^{2-}]$ values) and low $[O]$ contents. Technologically, for the slag types we have studied, we recommend the maximum FeO content to be 1.5% and the maximum MnO content to be 1.0%.

From the above mentioned things, we can see the significant influence of the chemical composition on the desulphurisation process. We consider that this influence is manifested either by the action of the oxides on the slag viscosity (Al_2O_3 , TiO_2) or by the affinity of some cautions (Ca, Mg) to sulphur in slag.

For each correlation, we determined the equation of the regression curve, along with the equations afferent to the curves that bound the variation range (both upper and lower limits).

By processing the data in the MATLAB program, we obtained multiple correlation equations and, by graphically represented them, we obtained the correlation surfaces. To establish the optimum chemical composition range, we analysed the regression surfaces for finding the value of the L.S., desirable above the average value obtained from the data afferent to the analysed heats.

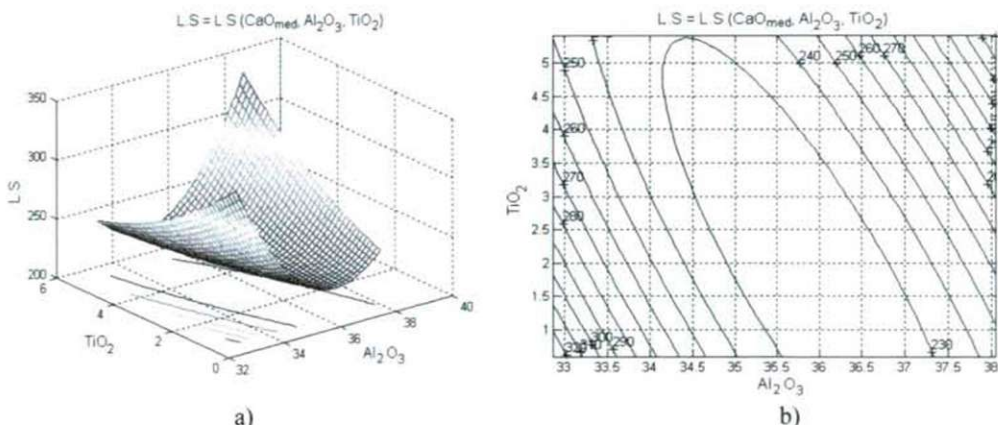


Fig.8 The variation of the sulphur distribution coefficient (L.S) versus the TiO_2 and Al_2O_3 content in slag: a) surface; b) contour lines

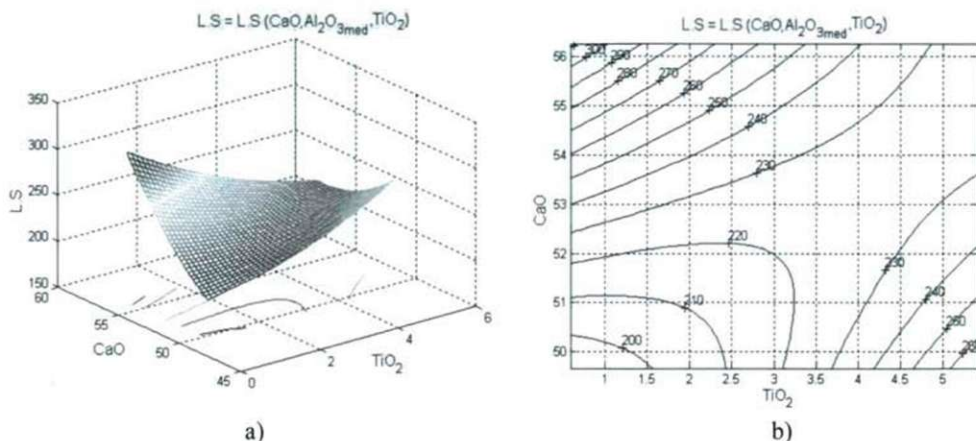


Fig.9 The variation of the sulphur distribution coefficient (*L.S*) versus the TiO_2 and CaO content in slag: a) surface; b) contour lines

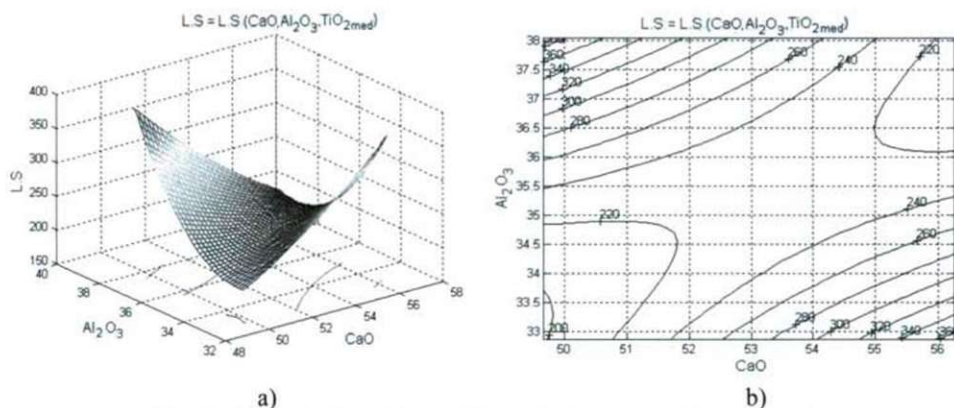


Fig.10 The variation of the sulphur distribution coefficient (*L.S*) versus the CaO and Al_2O_3 content in slag: a) surface; b) contour lines

4. CONCLUSIONS

Based on the experiments, on the results obtained from data processing and on the technical analysis of these data, we concluded the followings:

- From a technological point of view, the slag types used in our experiments met our needs, mainly due to their adequate fluidity;
- The chemical composition of the slag has a significant influence on the L.S., either indirectly, due to the viscosity, or directly, due to the affinity of the oxide cautions to the sulphur anions;
- We consider that it is possible to obtain very good results in the desulphurisation process by using synthetic slag having the following chemical composition: ...;

- Based on the results obtained during the laboratory phase, we believe that good results can be achieved under industrial conditions, too. So, we propose to perform such experiments in a future stage.

REFERENCES

1. Vacu, S., ș.a., Elaborarea oțelurilor aliate vol. I, Ed. Tehnică, București, 1980.
2. Vacu, S., ș.a., Elaborarea oțelurilor aliate vol. II, Ed. Tehnică, București, 1980.
3. Tripșa, I. Pumnea, C., Dezoxidarea oțelurilor, Ed. Tehnică, București, 1981.
4. Hepuț, T., Ardelean, E., Kiss, I., Some influence of the viscosity of synthetic slags used in continuous steel casting, Revista de Metalurgia 41(3), Madrid, 2005.
5. Hepuț, T., Ardelean, E., Socalici, A., Maksay, St. Găvănescu, A., Steel desulphurization with synthetic slag, Revista de Metalurgia 43(3), Madrid, 2007.